

Electron spin relaxation in semiconductors and semiconductor structures

Yu.G.Semenov

*Groupe d'Etude des Semi-Conducteurs, Université Montpellier 2,
Place Eugène Bataillon, 34095 Montpellier, France
(February 6, 2008)*

We suggest an approach to the problem of free electron spin evolution in a semiconductor with arbitrary anisotropy or quantum structure in a magnetic field. The developed approach utilizes quantum kinetic equations for average spin components. These equations represent the relaxation in terms of correlation functions for fluctuating effective fields responsible for spin relaxation. In a particular case when autocorrelation functions are dominant, the kinetic equations reduce to the Bloch equations. The developed formalism is applied to the problem of electron spin relaxation due to exchange scattering in a semimagnetic quantum well (QW) as well as to the spin relaxation in a QW due to Dyakonov-Perel mechanism. The results permit to separate the longitudinal T_1 and transversal T_2 relaxations times in a strong enough magnetic field and to trace the cases of undistinguished parameters T_1 and T_2 in zero and small magnetic fields. Some new predictions of the developed theory are discussed.

I. INTRODUCTION

The achievements in the investigations of ferromagnetism (FM) of diluted magnetic semiconductors (DMS) [1] and in spin injection technology [2] with the possibility to fabricate the spin-controlled devices have sparked renewed interest to studies of spin relaxation of electrons, holes and excitons (see [3] and references therein). During the recent years, the optical picosecond technique acquire ability to observe the electron and hole spin kinetics in semiconductor quantum structures over wide range of temperatures and magnetic fields [4], [5]. In spite of intensive work the spin relaxation processes are still not fully understood in these structures. One of the reasons is the deficiencies in the present theories. If, for example, the theory of giant spin splitting of the electron states in DMS has a good base in terms of molecular exchange field, [6], spin relaxation theory has, by now, a huge gap between phenomenological and microscopic approaches to this problem.

The phenomenological description of carrier or exciton spin relaxation in semiconductors is commonly started with Hamiltonian H_d without dissipation terms responsible for spin relaxation. For a particle with spin S (electron, exciton, etc.), the number of equations for average spin values $A_I = \langle S_X^k S_Y^l S_Z^m \rangle$ (subscripts denote Cartesian components; k, l, m satisfy the condition $1 \leq k + l + m \leq 2S$; symbol I marks all indexes in the right hand part of A_I) is finite and is determined by the equations of motion ($\hbar = 1$)

$$\frac{dA_I}{dt} = -i[A_I, H_d]. \quad (1)$$

The system (1) describes the evolution of spin system without relaxation. To take it into consideration we

should include the relaxation part R_I to the Eq. (1). Generally speaking, the relaxation of each A_I to thermal equilibrium value A_J^0 might depend on full set of spin averages. Therefore relaxation part reads

$$R_I = - \sum_J \frac{(A_I - A_J^0)}{\tau_{I,J}}. \quad (2)$$

Sometimes, the number of relaxation parameters $\tau_{I,J}^{-1}$ can be reduced due to the presence of specific physical mechanisms (see, for example, [7]). Nevertheless, it should be mentioned that a general procedure (for estimation of magnitudes of all relaxation parameters) that allows to reduce the numbers of relaxation terms (2) is absent.

Other problem arises when one tries to relate the parameters $\tau_{I,J}^{-1}$ with the spin-flip rate W (this is the aim of most microscopic calculations based on different known relaxation mechanisms). To clarify this problem we consider Bloch equations for average spin components S_μ in a magnetic field directed along OZ axis

$$\frac{d}{dt} \begin{pmatrix} S_X \\ S_Y \\ S_Z \end{pmatrix} = \omega \begin{pmatrix} -S_Y \\ S_X \\ 0 \end{pmatrix} - \begin{pmatrix} S_X/T_2 \\ S_Y/T_2 \\ (S_Z - S_Z^0)/T_1 \end{pmatrix}. \quad (3)$$

Eqs (3) looks like Eq.(1),(2), where S_Z^0 is a thermal equilibrium value of S_Z , ω is Zeeman splitting in a magnetic field. Eqs (3) involve two relaxation times, the longitudinal T_1 and transversal T_2 . In the framework of phenomenological Eqs (3) it is not apparent how the parameters T_1 and T_2 having different physical meaning are related to spin-flip probability W . Moreover, the transformation from the case of $T_1 = T_2$ at zero magnetic field ($\omega = 0$) to the case $T_1 \neq T_2$ at $\omega \neq 0$ cannot be traced both with the help of Eqs (3) and by the microscopic calculations of spin-flip rate W .

The present work is an attempt to "fill the gap" between the phenomenological approach to spin relaxation and microscopic calculations of spin flip rates in the case of electron relaxation with spin 1/2 in a semiconductor. To do that, we derive the quantum kinetic equations for density matrix of spin 1/2. The equations have been derived in terms of correlation functions of dissipative subsystem. Despite the presence of some symmetry of correlation parameters, the kinetic equations can be only reduced to the form that remains, nevertheless, more complicated than Bloch equations. In the following sections the developed theory is applied to electron exchange scattering on the magnetic ions in a semimagnetic quantum well (QW). Then, Dyakonov-Perel mechanism is considered with respect to anisotropy of relaxation times in a QW and their reduction in a magnetic field. We discuss also the possible applications of the results obtained here.

II. BASIC EQUATION FOR DENSITY MATRIX

Let the electron spins represent a *small part* of total system so that all other variables is related to the bath being at thermal equilibrium. Corresponding Hamiltonian reads

$$H = H_S^0 + H_L + H_{SL}. \quad (4)$$

Here H_S^0 , H_L , and H_{SL} are, respectively, the Hamiltonians of electron spin, dissipative subsystem (assumed to be at thermal equilibrium with a bath at a temperature T), and their interaction. According to projection operator method (Ref. [8]) the density matrix of the system (4) is expressed in terms of main part and the rest:

$$\rho = f\sigma + \eta, \quad (5)$$

where

$$\begin{aligned} \sigma &= \text{Tr}_L \rho; \\ f &= \frac{\exp(-\beta H_L)}{\text{Tr}_L \exp(-\beta H_L)}; \\ \eta &= P\rho \equiv (1 - f\text{Tr}_L)\rho. \end{aligned}$$

We are looking for the kinetic equation for reduced density matrix σ with the Hamiltonian

$$H = H_S + H_L + V, \quad (6)$$

where

$$\begin{aligned} H_S &= H_S^0 + \langle H_{SL} \rangle; \\ V &= H_{SL} - \langle H_{SL} \rangle, \end{aligned} \quad (7)$$

so that $\langle V \rangle = 0$, where $\langle \dots \rangle = \text{Tr}_L f \dots$.

It can be shown that exact form of equation for the σ is

$$\frac{d\sigma}{dt} = -i\mathcal{H}_S\sigma - \mathcal{C}(\sigma) - i\mathcal{D}(\rho(0));$$

with

$$\begin{aligned} \mathcal{C}(\sigma) &= \text{Tr}_L \mathcal{V} \int_0^t \mathcal{S}(t, t') \mathcal{V} f\sigma(t') dt', \\ \mathcal{D}(\rho(0)) &= \text{Tr}_L \mathcal{V} \mathcal{S}(t, 0) P\rho(0), \\ \mathcal{S}(t, t') &= \exp \left\{ -i \int_{t'}^t (\mathcal{H}_S(\tau) + \mathcal{H}_L + P\mathcal{V}) d\tau \right\}. \end{aligned} \quad (8)$$

Here the calligraphic letters mean the Liouville operators introduced over operator space as $\mathcal{H}_S\sigma = [H_S, \sigma]$, etc. The term $\mathcal{D}(\rho(0))$ vanishes for the initial condition $\rho(0) = f\sigma(0)$.

The expansion of Eq.(8) up to second order in the operator of interaction yields the kinetic equation for σ :

$$\frac{d\sigma(t)}{dt} = -i\mathcal{H}_S\sigma - \text{Tr}_L \int_0^t \mathcal{V}(t, t) \mathcal{V}(t, t') f\sigma(t) dt', \quad (9)$$

where

$$\begin{aligned} V(t, t') &= \exp \left\{ -i \int_{t'}^t H_S(\tau) d\tau \right\} \times \\ &\times V(t) \exp \left\{ i \int_{t'}^t H_S(\tau) d\tau \right\}, \end{aligned} \quad (10)$$

$$V(t) = \exp \{ iH_L t \} V \exp \{ -iH_L t \}. \quad (11)$$

We consider the reduced density matrix $\sigma(t)$ at the long enough time scale (as compared to times of attainment of a thermal equilibrium of dissipative subsystem). Thus, the upper limit of integration in Eq. (9) can be extended to infinity. Under this assumption we obtain Markovian equation for $\sigma(t)$, providing that spin relaxation times T are sufficiently longer than correlation times τ of dissipative system responsible for spin relaxation.

To rewrite Eq.(9) in the matrix form, we should use some base. As the base, here we use the eigenvectors of spin operator S_Z . For $S = 1/2$, the most general form of interaction is: [9]

$$H_{SL} = \mathbf{S}\mathbf{\Omega}, \quad (12)$$

while electron spin-Hamiltonian can be written as

$$H_S = \omega S_Z, \quad (13)$$

ω is the spin splitting in a magnetic field. Eq. (13) can be considered also as a definition of OZ axis as quantization direction. Substitution of Eq.(12) to Eq.(9) (at $t \rightarrow \infty$), permits to express the collision integral in terms of the different Fourier components of correlation functions for Ω_α . Their number can be reduced with respect to the spectral properties of correlation functions and to

the following identities (valid for any operators A and B):

$$\langle A(\tau) B \rangle_\omega = e^{-\beta\omega} \langle B(\tau) A \rangle_{-\omega} = e^{-\beta\omega} \langle BA(\tau) \rangle_\omega, \quad (14)$$

where the definitions of $A(t)$ and $B(t)$ are similar to Eq. (11); $\beta = 1/T$. The definition of Fourier transformation of correlation function is

$$\langle A(\tau) B \rangle_\omega = \frac{1}{2\pi} \int_{-\infty}^{\infty} \langle A(\tau) B \rangle e^{i\omega\tau} d\tau. \quad (15)$$

It is convenient to introduce the average values of spin components instead of density matrix σ :

$$\begin{aligned} \langle S_X \rangle &\equiv \mathbf{X} = \text{Tr} \sigma S_X, \\ \langle S_Y \rangle &\equiv \mathbf{Y} = \text{Tr} \sigma S_Y, \\ \langle S_Z \rangle &\equiv \mathbf{Z} = \text{Tr} \sigma S_Z. \end{aligned} \quad (16)$$

Straightforward calculations with the aid of Eqs(14,15) yield following system of equations for components of $\langle \mathbf{S} \rangle$:

$$\frac{d}{dt} \begin{pmatrix} \mathbf{X} \\ \mathbf{Y} \\ \mathbf{Z} \end{pmatrix} = \omega \begin{pmatrix} -\mathbf{Y} \\ \mathbf{X} \\ 0 \end{pmatrix} - \mathbf{\Gamma} \begin{pmatrix} \mathbf{X} \\ \mathbf{Y} \\ \mathbf{Z} - \mathbf{Z}_0 \end{pmatrix}, \quad (17)$$

where relaxation matrix $\mathbf{\Gamma}$ is determined via correlation functions

$$\gamma_{\mu\nu}(\omega) = \langle \Omega_\mu(\tau) \Omega_\nu \rangle_\omega. \quad (18)$$

Equation (17) describes the relaxation of spin 1/2 to its equilibrium state $\mathbf{X}(t) \xrightarrow{t \rightarrow \infty} \mathbf{X}_0$, $\mathbf{Y}(t) \xrightarrow{t \rightarrow \infty} \mathbf{Y}_0$, and $\mathbf{Z}(t) \xrightarrow{t \rightarrow \infty} \mathbf{Z}_0$, with $\mathbf{X}_0 = \mathbf{Y}_0 = 0$, and

$$\mathbf{Z}_0 = -\frac{1}{2} \tanh \frac{\beta\omega}{2}. \quad (19)$$

The general form of relaxation matrix $\mathbf{\Gamma}$ is quite complex. Below, we consider two important specific cases permitting to simplify the components of correlation matrix $\gamma_{\mu\nu}(\omega)$ (18); $\nu, \mu = X, Y, Z$. First, we assume that the matrix (18) is symmetric, $\gamma_{\mu\nu}(\omega) = \gamma_{\nu\mu}(\omega)$. Thus, the magnetic field influence on Hamiltonian of dissipative subsystem is disregarded (Ref. [10]). With respect to symmetric property of correlation function, one can obtain

$$\mathbf{\Gamma} = \frac{\pi}{\hbar} \begin{pmatrix} \gamma_{zz}^0 + n\gamma_{yy} & -n\gamma_{xy} & -n\gamma_{xz} \\ -n\gamma_{xy} & \gamma_{zz}^0 + n\gamma_{xx} & -n\gamma_{yz} \\ -n\gamma_{xz} & -n\gamma_{yz} & n(\gamma_{xx} + \gamma_{yy}) \end{pmatrix}; \quad (20)$$

$n \equiv n(\omega) = (1 + e^{\beta\omega})/2$, $\gamma_{\mu\nu} \equiv \gamma_{\mu\nu}(\omega)$, $\gamma_{\mu\nu}^0 \equiv \gamma_{\mu\nu}(0)$. Notice that Eqs(17),(20) are, generally spiking, derived for the case of anisotropic medium and arbitrary spin splitting ω .

In the case of zero spin splitting ($\omega = 0$) and isotropic medium, the relaxation matrix $\mathbf{\Gamma}$ (20) becomes symmetric. In this case, Eq.(20) are similar to those obtained in the work [9] in terms of fluctuating internal magnetic field $\mathbf{\Omega}$.

In the case of strong enough spin splitting, one can expect that $\gamma_{\alpha\alpha}(\omega) \ll \gamma_{zz}(0)$. If we introduce $T_1^{-1} = \pi n(\gamma_{xx}(\omega) + \gamma_{yy}(\omega))$ and $T_2^{-1} = \pi\gamma_{zz}(0)$, and omit the off-diagonal components of $\mathbf{\Gamma}$, the latter inequality permits to rewrite the Eq.(17) to the form of Bloch equations (3).

Second important case corresponds to antisymmetric coefficients $\gamma_{\mu\nu}(\omega) = -\gamma_{\nu\mu}(\omega)$ for $\nu \neq \mu$. In this case we can obtain other form of relaxation matrix:

$$\mathbf{\Gamma} = \frac{\pi}{\hbar} \begin{pmatrix} \gamma_{zz}^0 + n\gamma_{yy} + ni\gamma_{xy} & 0 & ni\gamma_{yz} \\ 0 & \gamma_{zz}^0 + n\gamma_{xx} + ni\gamma_{xy} & ni\gamma_{zx} \\ 0 & 0 & n(\gamma_{xx} + \gamma_{yy} + i\gamma_{xy}) \end{pmatrix}. \quad (21)$$

In the limit of zero magnetic field, the coefficients $\gamma_{\mu\nu}(\omega \rightarrow 0)$ vanish if $\nu \neq \mu$; thus the Eq.(21) transforms to matrix (20) with zero off-diagonal components. The spectral properties (14) with respect to definition of $n(\omega)$ permits to observe that both relaxation matrix (21) and matrix (20) are even functions of the electron spin splitting ω : $\mathbf{\Gamma}(\omega) = \mathbf{\Gamma}(-\omega)$.

The Eqs (17) with definitions (20),(21) are the main result of theoretical background of the work. In derivation of kinetic equations (17) we assume neither any specific properties of heat bath with Hamiltonian H_L nor any specific interaction mechanism H_{eL} . We shall show

how Eqs (17) can be used in the particular cases corresponding to (20) and (21). The short review of the relations between correlation functions (15) and two-time temperature Green's functions (with well-known calculation technique) is presented in Appendix.

III. EXCHANGE SCATTERING ON MAGNETIC IONS IN THE 2D QW

Consider the problem of electron spin exchange scattering on the magnetic ions in a 2D quantum well (see

Ref. [11] [12]). The carrier-ion spin-spin interaction operator has the form of following contact interaction

$$H_{SL} = -\alpha \sum_j \mathbf{S}^j \mathbf{s}_e \delta(\mathbf{r} - \mathbf{R}_j), \quad (22)$$

where α is exchange integral, $\mathbf{S}^j$ is the magnetic ion spin at the site $\mathbf{R}_j$; $\mathbf{s}_e$ and $\mathbf{r}$ are the spin and coordinate of electron respectively. The sum is performed over all magnetic impurities. The Hamiltonian of dissipative subsystem include Zeeman energy of magnetic ions and the electron kinetic energy $\varepsilon_{\mathbf{k}}$ with in-plane wave vector $\mathbf{k}$. For simplicity sake, we restrict our consideration by the ground electronic confinement state only. So, the Hamiltonian is assumed to take the form:

$$H_L = \sum_j \omega_0 S_Z^j + \sum_{\mathbf{k}, \sigma} \varepsilon_{\mathbf{k}} a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}, \sigma}, \quad (23)$$

where ω_0 is the magnetic ion Zeeman splitting in a magnetic field directed along OZ axis; $a_{\mathbf{k}, \sigma}^\dagger$ and $a_{\mathbf{k}, \sigma}$ are the creation and annihilation operators; spin index σ is introduced to normalize the chemical potential for total numbers of electrons. In our case

$$\sum_{\mathbf{k}, \sigma} \langle a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}, \sigma} \rangle \equiv \sum_{\mathbf{k}, \sigma} f_{\mathbf{k}, \sigma} = 1. \quad (24)$$

Now we can perform the renormalization procedure (7) with operator (22) and represent (second-quantized) interaction V (12) in the form

$$\begin{aligned} \Omega_{X,Y} = & -\frac{\alpha}{S_0} \sum_{\substack{\mathbf{k}, \mathbf{k}', \sigma \\ \mathbf{k} \neq \mathbf{k}'}} \sum_j S_{X,Y}^j |\psi_\perp(\mathbf{R}_j)|^2 \times \\ & \times e^{i(\mathbf{k}-\mathbf{k}')\mathbf{R}_j} a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}', \sigma}, \end{aligned} \quad (25)$$

$$\Omega_Z = -\frac{\alpha}{S_0} \sum_{\substack{\mathbf{k}, \mathbf{k}', \sigma \\ \mathbf{k} \neq \mathbf{k}'}} \sum_j S_Z^j |\psi_\perp(\mathbf{R}_j)|^2 e^{i(\mathbf{k}-\mathbf{k}')\mathbf{R}_j} a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}', \sigma}.$$

Here S_0 is an area of a sample, $\psi_\perp(\mathbf{R}_j)$ is a perpendicular (to a plane of a structure) component of confinement wave function. The term with $\mathbf{k} \neq \mathbf{k}'$ is excluded from Eq. (25) due renormalization procedure (7). This procedure yields following Hamiltonian of dynamic subsystem:

$$H_S \equiv \omega s_{ez} = (\omega_e + G_{ez}) s_{ez}. \quad (26)$$

Eq.(26) defines spin splitting ω in a total field. This field consists of external magnetic field (with Zeeman frequency ω_e) and exchange molecular field

$$\begin{aligned} \mathbf{G}_e = & -\frac{\alpha}{S_0} \sum_j \langle \mathbf{S}^j \rangle |\psi(\mathbf{z}_j')|^2 = \\ = & -\alpha \langle \mathbf{S} \rangle \int_{-\infty}^{\infty} n_m(z') |\psi(z')|^2 dz'. \end{aligned} \quad (27)$$

Here $n_m(z')$ is a local concentration of magnetic ions that is assumed to be the function of coordinate z directed along the growth axis Z' . In the case of magnetic QW with width L_w and non-magnetic barriers, the integration should be performed between $-L_w/2$ and $L_w/2$, while $n_m(z)$ should be replaced by average concentration n_m in the QW.

We are looking for the Fourier transformation of Green's function

$$\gamma_{\mu, \nu}(\omega) = \langle \Omega_\mu(t); \Omega_\nu \rangle_\omega,$$

which (according to Eq. (25)) equals to

$$\gamma_{\mu, \nu}(\omega) = \frac{\alpha^2}{S_0^2} \sum_{\mathbf{k}, \mathbf{k}', \sigma} \sum_{\mathbf{k}_1, \mathbf{k}_1', \sigma_1} \sum_{j, j'} |\psi(z_j)|^2 |\psi(z_{j'})|^2 e^{i(\mathbf{k}-\mathbf{k}')\mathbf{R}_j + i(\mathbf{k}_1-\mathbf{k}_1')\mathbf{R}_{j'}} K_{\mathbf{k}, \sigma; \mathbf{k}', \sigma; \mathbf{k}_1, \sigma_1; \mathbf{k}_1', \sigma_1}^{\mu, j; \nu, j'}(\omega),$$

where

$$\begin{aligned} K_{\mathbf{k}, \sigma; \mathbf{k}', \sigma; \mathbf{k}_1, \sigma_1; \mathbf{k}_1', \sigma_1}^{\mu, j; \nu, j'}(\omega) = \\ = \left\langle S_\mu^j a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}', \sigma}(t); S_\nu^{j'} a_{\mathbf{k}_1, \sigma_1}^\dagger a_{\mathbf{k}_1', \sigma_1}(t) \right\rangle_\omega. \end{aligned} \quad (28)$$

The explicit form for equation of motion (A4) for the correspondent Green's function $\omega G_q^{\mu, \nu}(\mu, \nu = X, Y, Z; q$ is a rest of indexes that determines the correlation function (28)) is approximated by the following system of equations

$$\omega G_q^{X, X}(\omega) = \frac{\delta_{j, j'} \delta_{\mathbf{k}, \mathbf{k}_1'} \delta_{\mathbf{k}', \mathbf{k}_1} \delta_{\sigma, \sigma'}}{2\pi} \langle S_X^2 \rangle [f_{\mathbf{k}, \sigma}(1 - f_{\mathbf{k}', \sigma}) + f_{\mathbf{k}', \sigma}(1 - f_{\mathbf{k}, \sigma})] + \quad (29)$$

$$\begin{aligned} + (\varepsilon_{\mathbf{k}'} - \varepsilon_{\mathbf{k}}) G_q^{X, X}(\omega) - i\omega_0 G_q^{Y, X}(\omega); \\ \omega G_q^{Y, X}(\omega) = i \frac{\delta_{j, j'} \delta_{\mathbf{k}, \mathbf{k}_1'} \delta_{\mathbf{k}', \mathbf{k}_1} \delta_{\sigma, \sigma'}}{2\pi} \frac{\langle S_Z \rangle}{2} [f_{\mathbf{k}', \sigma} - f_{\mathbf{k}, \sigma}] + (\varepsilon_{\mathbf{k}'} - \varepsilon_{\mathbf{k}}) G_q^{Y, X}(\omega) + i\omega_0 G_q^{X, X}(\omega); \end{aligned} \quad (30)$$

where we use $\langle S_X S_Y \rangle = -\langle S_Y S_X \rangle = i \langle S_Z \rangle / 2$; the occupation numbers $f_{\mathbf{k},\sigma}$ are determined by Eq.(24). According to Eq.(A3), the imaginary part of the $G_q^{\mu,\nu}$ is

important for calculation of Γ . So, taking into account that $\omega = \omega + i\epsilon$ with infinitesimal ϵ , one can use following identity in the solution of Eqs (29,30):

$$\begin{aligned} \frac{\omega - (\epsilon' - \epsilon)}{[\omega - (\epsilon' - \epsilon)]^2 - \omega_0^2} &\rightarrow -i\frac{\pi}{2} [\delta(\omega - (\epsilon' - \epsilon) - \omega_0) + \delta(\omega - (\epsilon' - \epsilon) + \omega_0)]; \\ \frac{\omega_0}{[\omega - (\epsilon' - \epsilon)]^2 - \omega_0^2} &\rightarrow -i\frac{\pi}{2} [\delta(\omega - (\epsilon' - \epsilon) - \omega_0) - \delta(\omega - (\epsilon' - \epsilon) + \omega_0)]. \end{aligned} \quad (31)$$

The final result for Fourier transformation of correlation function looks like

$$\begin{aligned} K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;X,j'}(\omega) &= \frac{i}{2n} (G_q^{X,X}(\omega + i\epsilon) - G_q^{X,X}(\omega - i\epsilon)); \\ K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;X,j'}(\omega) &= \frac{\delta_{j,j'}\delta_{\mathbf{k},\mathbf{k}'_1}\delta_{\mathbf{k}',\mathbf{k}_1}\delta_{\sigma,\sigma_1}}{4n} \left\{ \langle S_X^2 \rangle [f_{\mathbf{k},\sigma}(1 - f_{\mathbf{k}',\sigma}) + f_{\mathbf{k}',\sigma}(1 - f_{\mathbf{k},\sigma})] \times \right. \\ &\times [\delta(\omega - (\epsilon' - \epsilon) - \omega_0) + \delta(\omega - (\epsilon' - \epsilon) + \omega_0)] + \\ &+ \frac{\langle S_Z \rangle}{2n} [f_{\mathbf{k}',\sigma} - f_{\mathbf{k},\sigma}] [\delta(\omega - (\epsilon' - \epsilon) - \omega_0) - \delta(\omega - (\epsilon' - \epsilon) + \omega_0)] \left. \right\}; \\ K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;X,j'}(\omega) &= \frac{i}{4n} \delta_{j,j'} \delta_{\mathbf{k},\mathbf{k}'_1} \delta_{\mathbf{k}',\mathbf{k}_1} \delta_{\sigma,\sigma_1} \left\{ \frac{\langle S_Z \rangle}{2} [f_{\mathbf{k}',\sigma} - f_{\mathbf{k},\sigma}] \times \right. \\ &\times [\delta(\omega - (\epsilon' - \epsilon) - \omega_0) + \delta(\omega - (\epsilon' - \epsilon) + \omega_0)] + \\ &+ \frac{\langle S_X^2 \rangle}{n} [f_{\mathbf{k},\sigma}(1 - f_{\mathbf{k}',\sigma}) + f_{\mathbf{k}',\sigma}(1 - f_{\mathbf{k},\sigma})] [\delta(\omega - (\epsilon' - \epsilon) - \omega_0) - \delta(\omega - (\epsilon' - \epsilon) + \omega_0)] \left. \right\}. \end{aligned} \quad (32)$$

$$\begin{aligned} K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;Y,j'}(\omega) &= K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;X,j'}(\omega) \text{ and } \\ K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;Y,j'}(\omega) &= -K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;X,j'}(\omega). \text{ Later equality shows that the exchange scattering corresponds just to the case of relaxation matrix (21). Direct calculation of off-diagonal matrix elements shows that } \\ K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;Z,j'}(\omega) &= K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;Z,j'}(\omega) = 0 \text{ since } \langle S_X \rangle = \langle S_Y \rangle = 0. \text{ In a similar manner, one can find} \end{aligned} \quad (33)$$

with $\epsilon = \epsilon_{\mathbf{k}}, \epsilon' = \epsilon_{\mathbf{k}'}$.

We assume that neither 2D structure stress, nor internal magnetic field affects the transversal magnetization (which means $\langle S_X^2 \rangle = \langle S_Y^2 \rangle$). Thus $K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;Y,j'}(\omega) = K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;X,j'}(\omega)$ and $K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;Y,j'}(\omega) = -K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;X,j'}(\omega)$. Later equality shows that the exchange scattering corresponds just to the case of relaxation matrix (21). Direct calculation of off-diagonal matrix elements shows that $K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{X,j;Z,j'}(\omega) = K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Y,j;Z,j'}(\omega) = 0$ since $\langle S_X \rangle = \langle S_Y \rangle = 0$. In a similar manner, one can find

$$\begin{aligned} K_{\mathbf{k},\sigma;\mathbf{k}',\sigma;\mathbf{k}_1,\sigma_1;\mathbf{k}'_1,\sigma_1}^{Z,j;Z,j'}(0) &= \frac{1}{2} \delta_{j,j'} \delta_{\mathbf{k},\mathbf{k}'_1} \delta_{\mathbf{k}',\mathbf{k}_1} \delta_{\sigma,\sigma_1} \langle S_Z^2 \rangle \times \\ &\times [f_{\mathbf{k},\sigma}(1 - f_{\mathbf{k}',\sigma}) + f_{\mathbf{k}',\sigma}(1 - f_{\mathbf{k},\sigma})] \delta(\epsilon' - \epsilon). \end{aligned} \quad (34)$$

The relaxation parameters in the matrix (21) can now be obtained with the help of (32,33). Eq.(24) reads now

$$\sum_{\sigma} f_{\mathbf{k},\sigma} = \frac{2\pi\hbar^2}{S_0 m T} e^{-\epsilon_{\mathbf{k}}/T}, \quad (35)$$

where m is the in-plane effective mass of the carriers. Substitution of Eq.(34) to the formula $\pi n \langle \Omega_Z(\tau) \Omega_Z \rangle_0$ gives following result in the case of $f_{\mathbf{k},\sigma} \ll 1$:

$$\pi\gamma_{zz}^0 = \pi \frac{\alpha^2}{S_0^2} \sum_{\mathbf{k},\mathbf{k}',\sigma}^{(\mathbf{k} \neq \mathbf{k}')} \sum_j \langle S_Z^2 \rangle |\psi(z_j)|^4 [f_{\mathbf{k},\sigma} + f_{\mathbf{k}',\sigma}] \delta(\epsilon - \epsilon'). \quad (36)$$

Calculation of sums in Eq.(36) yields

$$\frac{\pi}{\hbar} \gamma_{zz}^0 = I \frac{\alpha^2 m}{2L_w \hbar^3} n_m \langle S_Z^2 \rangle, \quad (37)$$

where dimensionless parameter I reflects the overlap of ψ -function and magnetic ions:

$$I = L_w \int_{-\infty}^{\infty} \frac{n_m(z')}{n_m} |\psi(z')|^4 dz' \quad (38)$$

In the case of infinitely deep QW containing the magnetic ions with concentration n_m , the integration in (38) gives $I = 3/2$.

To obtain other elements of the matrix (21) we should find γ_{xx} and γ_{xy} according to Eqs(32),(33). It can be shown that contribution of a second term in Eq.(32) is less then that of first one, while $\gamma_{xy} \ll \gamma_{xx} = \gamma_{yy}$, so that we can find

$$\pi n \gamma_{xx} = \pi \frac{\alpha^2}{S_0^2} \sum_{\mathbf{k}, \mathbf{k}', \sigma}^{\mathbf{k} \neq \mathbf{k}'} \sum_j \frac{\langle S_X^2 \rangle}{2} |\psi(z_j)|^4 [f_{\mathbf{k}, \sigma} + f_{\mathbf{k}', \sigma}] [\delta(\omega - (\varepsilon - \varepsilon') - \omega_0) + \delta(\omega - (\varepsilon - \varepsilon') + \omega_0)]. \quad (39)$$

Sums in Eq.(39) are evaluated similar to those in Eq.(36):

$$\frac{\pi}{\hbar} n \gamma_{xx} = I \frac{\alpha^2 m}{L_w \hbar^3} n_m \frac{\langle S_X^2 \rangle}{2} F\left(\frac{\omega}{T}, \frac{\omega_0}{T}\right), \quad (40)$$

where we introduce the function

$$F(x, y) = \frac{1}{4} [2 + \exp(-|x + y|) + \exp(-|x - y|)] \quad (41)$$

that decreases monotonically from 1 to 1/2 and reflects the suppression of electron spin fluctuations by a magnetic field. Thus, the kinetic equations(21) transforms to the Bloch equations(3) with following relaxation parameters

$$\frac{1}{T_1} = I \frac{\alpha^2 m}{L_w \hbar^3} n_m \langle S_X^2 \rangle F\left(\frac{\omega}{T}, \frac{\omega_0}{T}\right), \quad (42)$$

$$\frac{1}{T_2} = I \frac{\alpha^2 m}{L_w \hbar^3} n_m \left\{ \frac{\langle S_Z^2 \rangle}{2} + \frac{\langle S_X^2 \rangle}{2} F\left(\frac{\omega}{T}, \frac{\omega_0}{T}\right) \right\}. \quad (43)$$

The right hand parts of Eqs (37) and (40) equal to those of Eqs (42) and (43) respectively at zero magnetic field as it should be expected. Moreover, as $\omega \rightarrow 0, \omega_0 \rightarrow 0$, Eqs (42),(43) transform just to the double rate W of spin flip relaxation obtained with Golden Fermi Rule. [11], [12]

With magnetic field increasing, one can obtain in the limit $\omega, \omega_0 \gg T$,

$$\frac{T_1}{T_2} = 2S + \frac{1}{2}. \quad (44)$$

Eq.(44) shows that rate of phase relaxation exceeds the longitudinal relaxation rate with factor about one order of magnitude in the case of ions Mn^{2+} ($S = 5/2$). In the case of equidistant Zeeman splitting ω_0 of the magnetic ions, the magnetic field dependence of spin square averages is:

$$\begin{aligned} \langle S_X^2 \rangle &= \frac{1}{2} \coth \frac{\omega_0}{2T} b_S\left(\frac{\omega_0}{T}\right), \\ \langle S_Z^2 \rangle &= S(S+1) - 2 \langle S_X^2 \rangle, \end{aligned} \quad (45)$$

where $b_S(x) = -\langle S_Z \rangle = SB_S(Sx)$ is non-normalized Brillouin function:

$$b_S(x) = \left(S + \frac{1}{2}\right) \coth\left(S + \frac{1}{2}\right)x - \frac{1}{2} \coth \frac{x}{2} \quad (46)$$

Figure 1 shows the magnetic field dependence of the longitudinal and transversal relaxation times calculated

with the help of Eqs (42), (43), (45), (46). One can see that magnetic field suppresses the longitudinal relaxation while it enhances transversal relaxation for $S > 1/2$. In the limit of saturated magnetic field, $\omega, \omega_0 \gg T$, the decreasing of T_2 reaches the factor $\frac{2}{3} \frac{S+1}{S+1/2}$. Note, that the decreasing of transversal relaxation time in a magnetic field was observed for Mn spins but was not explained till now.

At the end of this section we estimate the relaxation time of the electron in $Cd_{1-x}Mn_xTe$ QW with $x=0.017$ and $L_w = 8$ nm. At zero magnetic field one can find $\tau_e = 5$ ps that is quite close to experimental value observed recently via time resolved magneto-optic Kerr effect. [13]

IV. DYAKONOV-PEREL MECHANISM

In a number of works [14], [15], [9], it have been shown that a fluctuating effective magnetic field accompanying the electron momentum scattering in the semiconductors with non-centrosymmetric lattice results in rather efficient spin relaxation. In this section we show how Dyakonov-Perel mechanism can be incorporated into formalism developed above.

Hamiltonian of dissipative subsystem is assumed to have the form

$$H_L = \sum_{\mathbf{k}, \sigma} \varepsilon_{\mathbf{k}} a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}, \sigma} + \sum_{\mathbf{k}, \mathbf{k}', \sigma} V_{\mathbf{k}, \mathbf{k}'} a_{\mathbf{k}, \sigma}^\dagger a_{\mathbf{k}', \sigma}. \quad (47)$$

Second term in Eq.(47) has symbolic meaning: we assume $V_{\mathbf{k}, \mathbf{k}'}$ to be an operator responsible for electron scattering by the impurities, phonons, or electron-electron collisions. We should also introduce the electron scattering changing randomly an effective magnetic field $\mathbf{B} = \mathbf{b}(\mathbf{k})/\mathbf{g}_e \mu$ that corresponds to band spin splitting

$$H_{int} = \sum_{\mathbf{k}, \sigma} \mathbf{s}_e \mathbf{b}(\mathbf{k}) \mathbf{a}_{\mathbf{k}, \sigma}^\dagger \mathbf{a}_{\mathbf{k}, \sigma}. \quad (48)$$

Therefore, the operator of this field reads

$$\Omega_\mu = \sum_{\mathbf{k}, \sigma} b_\mu(\mathbf{k}) \mathbf{a}_{\mathbf{k}, \sigma}^\dagger \mathbf{a}_{\mathbf{k}, \sigma}. \quad (49)$$

The specific form of the function $b_\mu(\mathbf{k})$ is determined by a band Hamiltonian (see, for instance, Ref. [9]) and depends on dimensionality of the system under consideration (Ref. [15]).

We introduce the Green's function

$$\tilde{G} \equiv \tilde{G}_{2,3} = \left\langle \left\langle a_{\mathbf{k}_2}^\dagger a_{\mathbf{k}_3}; a_{\mathbf{k}_1}^\dagger a_{\mathbf{k}_1} \right\rangle \right\rangle_\omega. \quad (50)$$

For simplicity, here we suppress spin indices while $1 \equiv \mathbf{k}_{1,2} \equiv \mathbf{k}_2$, etc. Equation (A4) with Hamiltonian (47) assumes the form

$$[\omega - (\varepsilon_1 - \varepsilon_2)] \tilde{G}_{2,3} = \frac{\delta_{2,1} \delta_{3,1}}{\pi} f_1(1 - f_1) + \sum_4 \left(V_{3,4} \tilde{G}_{2,4} - V_{4,2} \tilde{G}_{4,3} \right). \quad (51)$$

We are looking for $\tilde{G}_{1,1}$ that can be represented via $\tilde{G}_{2,3}$. Solution of the Eq.51 depends strongly on $\mathbf{k}, \mathbf{k}'$ - dependences of operators $V_{\mathbf{k},\mathbf{k}'}$. We assume that following general relation for Green's function holds (Ref. [18])

$$\tilde{G}_{1,1} = \frac{f_1(1 - f_1)}{\pi(\omega + i\Gamma_{1,1})}, \quad (52)$$

where $\Gamma_{1,1}$ means the rate of electron moment relaxation due to scattering processes described by second term in the Eq.(47). Thus, the relaxation parameters are defined by

$$\frac{\pi}{\hbar} n \gamma_{\mu,\nu} = \sum_{\mathbf{k}} b_\mu(\mathbf{k}) \mathbf{b}_\nu(\mathbf{k}) \frac{\mathbf{\Gamma}_{\mathbf{k},\mathbf{k}}/\hbar}{\hbar^2 \omega^2 + \mathbf{\Gamma}_{\mathbf{k},\mathbf{k}}^2}. \quad (53)$$

Let us consider the electron spin splitting caused by k^3 - terms in band Hamiltonian (Ref. [14]). This mechanism had been considered for 2D-electron gas in the work [15]. If external magnetic field is directed along the axis of structure growth, one can obtain

$$b_\mu(\mathbf{k}) = \mathbf{r}_\alpha \kappa_\mu \quad (54)$$

with

$$r_\alpha = \frac{\alpha \hbar^3}{m^{3/2} (2E_g)^{1/2}}, \quad (55)$$

$$\kappa_x = -k_x q^2; \kappa_y = k_y q^2; \kappa_z = 0, \quad (56)$$

where m is in-plane effective mass, q^2 is defined via electron ψ - function confined in a QW,

$$q^2 = \left\langle \psi \left| -\frac{\partial^2}{\partial z^2} \right| \psi \right\rangle. \quad (57)$$

We see that only two components of relaxation parameters, $\gamma_{x,x}$ and $\gamma_{y,y}$ have nonzero values. The calculations with the help of Eq. (35) give rise to following expression for transversal relaxation time

$$\frac{1}{T_2} = \frac{\pi}{\hbar} n \gamma_{x,x} = \frac{\pi}{\hbar} n \gamma_{y,y} = \frac{\alpha^2 \hbar^2 q^4 T}{2m^2 E_g} \frac{\tau_e}{1 + (\omega \tau_e)^2}, \quad (58)$$

where the electron scattering time is defined via averaged value of $\Gamma_{\mathbf{k},\mathbf{k}}$:

$$\tau_e^{-1} = \hbar^{-1} \langle \Gamma_{\mathbf{k},\mathbf{k}} \rangle. \quad (59)$$

Note that approximation (59) is not necessary for calculations of T_1 and T_2 . The dependence $\tau_e(\mathbf{k})$ can be taken into account for more accurate theories (see Ref. [9]).

According to Eq.(20), the longitudinal relaxation rate is

$$\frac{1}{T_1} = \frac{\pi}{\hbar} n (\gamma_{x,x} + \gamma_{y,y}) = \frac{2}{T_2}. \quad (60)$$

We can see that T_1 can be shorter than T_2 in the systems with strong anisotropy.

Other important case corresponds to magnetic field directed along OZ axis in QW plane while OX axis is a perpendicular to this plane. One can find

$$\kappa_x = 0; \kappa_y = -k_y q^2; \kappa_z = k_z q^2. \quad (61)$$

In this case, three parameters describe electron spin relaxation:

$$\begin{aligned} \frac{1}{T_{2X}} &= \frac{\alpha^2 \hbar^2 q^4 T}{2m^2 E_g} \tau_e \left(1 + \frac{1}{1 + (\omega \tau_e)^2} \right), \\ \frac{1}{T_{2Y}} &= \frac{\alpha^2 \hbar^2 q^4 T}{2m^2 E_g} \tau_e, \\ \frac{1}{T_1} &= \frac{\alpha^2 \hbar^2 q^4 T}{2m^2 E_g} \frac{\tau_e}{1 + (\omega \tau_e)^2}. \end{aligned} \quad (62)$$

We can see that transversal relaxation (Eq.58) can be suppressed significantly by the strong enough magnetic field, $\omega \tau_e \gg 1$, due to dynamical averaging effect in the case of Faraday geometry of experiment [16]. In the case of Voigt configuration (Eqs (62)), magnetic field can suppress the transversal relaxation time by no more than two times. The effect of drastic magnetic anisotropy of spin relaxation in QWs can be used to recognize the specific mechanism under consideration. Actually, the typical scattering time of an electron in semiconductors is about $\tau_e \sim 10^{-12}$. To make the magnetic field anisotropy effect visible, one should apply quite strong magnetic field to non-magnetic structure. On the other hand, considered anisotropy effect can be amplified in DMS structures giving rise to inequality $\omega \gg \omega_0$ at moderate magnetic fields (Eqs (26), (27)).

V. CONCLUSIONS

In this work, we develop the microscopic theory of electron spin evolution in semiconductors in terms of quantum kinetic equations for arbitrary mechanism of spin relaxation. The relaxation term in these equations has been derived as a matrix of correlation functions providing relatively short correlation times (as compared to spin relaxation times, $\tau \ll T$) of dissipative subsystem. Our theory permits to distinguish the phase and energy relaxation processes and to capture the case of zero and small magnetic fields.

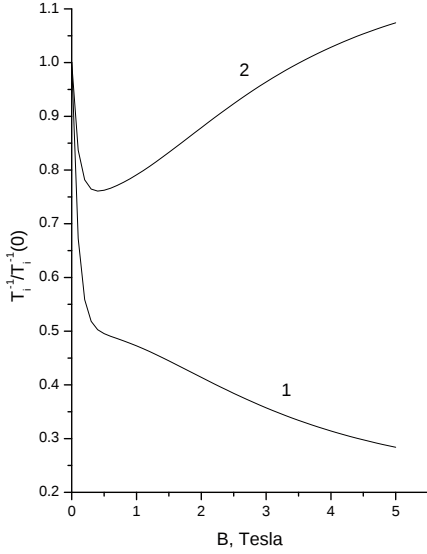


FIG. 1. Magnetic field dependencies of the rates of longitudinal ($i = 1$) and transversal ($i = 2$) electron spin relaxation at $T = 4K$ in $Cd_{1-x}Mn_xTe$ ($x = 0.017$) crystal.

We show that spin relaxation process due to exchange scattering in a semimagnetic QW determines the longitudinal and transversal spin relaxation times. Specific calculations of relaxation parameters show that only longitudinal relaxation can be described by flip-flop processes which is suppressed in a magnetic field. On the other hand, transversal relaxation is due to the effective exchange field fluctuations, which increase with magnetic field. Qualitatively, the latter effect has the same reason as growth of line width of spin flip Raman scattering by shallow donors in diluted magnetic semiconductors [17].

The theory has been successfully applied to Dyakonov-Perel mechanism of carrier spin relaxation in a QW. The significant difference in transversal relaxation rates for parallel and perpendicular (to growth axis) magnetic field orientations has been found.

Proposed approach to relaxation can be extended to any two-level system described by fictitious spin 1/2. From this standpoint, the analysis of heavy hole spin

relaxation in QW in terms of Eqs (17,20,21) promises new insight into this problem. The investigations of a hole relaxation in QWs or uniaxial semiconductors will be reported elsewhere.

VI. ACKNOWLEDGEMENT

Author would like to thanks D. Scalbert for fruitful discussions. This work was partially supported by the Grant No. 09244106 of the Ministry of Education and Science.

APPENDIX A:

Equation (17) reduces the problem of spin relaxation to calculations of correlation functions of operators Ω related to a heat bath at a thermal equilibrium. Theory of correlation functions for quantum-mechanical operators is well developed (see e.g. Ref. [18]). In this Appendix, we present few equations that are needed in subsequent analysis of relaxation parameters.

Introduce first two-time temperature retarded Green's function (Ref. [18])

$$G(t, t') \equiv \langle \langle \Omega_\mu; \Omega_\nu \rangle \rangle = -i\theta(t - t') \langle [\Omega_\mu(t), \Omega_\nu(t')] \rangle. \quad (A1)$$

The bracket $[\Omega_\mu(t), \Omega_\nu(t)]$ denotes a commutator or anticommutator for operators $\Omega_\mu(t)$ and $\Omega_\nu(t)$. Fourier transformation of Green's function (A1) reads

$$G(\omega) \equiv \langle \langle \Omega_\mu; \Omega_\nu \rangle \rangle_\omega = \frac{1}{2\pi} \int_{-\infty}^{\infty} G(t, 0) \exp(i\omega t) dt. \quad (A2)$$

Fourier transformation of correlation functions (Eq.(15)) can be expressed in terms of that for Green's functions Eq.(A2):

$$\gamma_{\mu\nu}(\omega) = i \lim_{\epsilon \rightarrow 0} \frac{G(\omega + i\epsilon) - G(\omega - i\epsilon)}{2n(\omega)}. \quad (A3)$$

So, the problem is reduced to explicit calculation of Green's functions in Eq.(A1). The equation of motion for their Fourier component is [18]:

$$\omega G(\omega) = \frac{1}{2\pi} \langle [\Omega_\mu, \Omega_\nu] \rangle + \langle \langle (\Omega_\mu H_L - H_L \Omega_\mu); \Omega_\nu \rangle \rangle_\omega. \quad (A4)$$

The solution of equation (A4) permit to find the correlation function, which, in turn, determines the spin relaxation according to Eqs (15), (20) and (21).

- [1] H. Ohno, *Science*, **281**, 951 (1998).
- [2] Y. Ohno, D. K. Young, B. Beschoten, F. Matsukura, H. Ohno, and D. D. Awschalom, *Nature (London)* **402**, 790, (1999).
- [3] For a recent review see L. Viña, *J. Physics: Condens. matter* **11**, 5929 (1999).
- [4] S.A. Crooker, J.J. Baumberg, F. Flack, et al., *Phys. Rev. Lett.* **77**, 2814 (1996).
- [5] S. A. Crooker, D. D. Awschalom, J. J. Baumberg, F. Flack, and N. Samarth, *Phys. Rev. B* **56**, 7574 (1997).
- [6] See, *Diluted magnetic semiconductors*, edited by J.K. Furdyna and J. Kossut, Vol. 25 of *Semiconductors and Semimetals* (Academic, Boston, 1988).
- [7] M. Dyakonov, X. Marie, T. Amand, P. Le Jeune, D. Robard, M. Brousseau, and J. Barrau, *Phys. Rev. B* **56**, 10412 (1997).
- [8] P. Zwanzig. *J.Chem.Phys.* **33**, 1338 (1960).
- [9] G.E. Pikus, A.N. Titkov, in book: *Optical Orientation*, Ed. F. Meier and B.P. Zakharchenia. Elsevier Science Publishers B.N., 1984.
- [10] L.D. Landau, E.M. Lifshits. *Electrodynamics of continuous media*, Pergamon Press, 1978.
- [11] G. Bastard and R. Ferreira, *Surface Science* **267**, 335 (1992).
- [12] Yu.G. Semenov, F.V. Kyrychenko. *Semicond. Sci. Technol.* **11**, 1268 (1996).
- [13] C. Camilleri, F. Teppe, D. Scalbert, Y.G. Semenov, M. Nawrocki, M. Dyakonov, J. Cibert, S. Tatarenko, T. Wojtowicz (*Phys. Rev. B*, to be published).
- [14] M.I. Dyakonov and V.I. Perel, *Zh. Exp. Teor. Fiz.* **60**, 1954 (1971) [*Sov. Phys. JETP* **33**, 1053 (1971)].
- [15] M.I. Dyakonov, V. Yu. Kachorovskii. *Fiz. Tech. Poluprovodn.* **20**, 178 (1986); [*Sov. Phys. Semicond.* **20**, 110 (1986)].
- [16] Spin-relaxation suppression due to freezing of orbital motion in a magnetic field is also important effect (see, E.L. Ivchenko. *Fiz. Tverd. Tela* **15**, 1566 (1973); [*Sov. Phys. Sol. State* **15**, 1048 (1973)]), which is not considered here.
- [17] S.M. Ryabchenko, Yu.G. Semenov, *Fiz. Tech. Poluprov.* **17**, 2040 (1983), [*Sov. Phys. Semicond.* **17**, 1301 (1983)].
- [18] D.N. Zubarev, *Uspekhi Fiz. Nauk*, **71**, 71 (1960).